

Product Data Sheet

steament® H-4

Fly Ash for Concrete according to DIN EN 450


steament® H-4 fly ash is a fine-grained construction material that mainly consists of dust-like, glassy particles. It is produced as a by-product from the process of combustion of hard coal to produce electricity and heat in the power plant “**Kraftwerk Herne**“. Its main constituents are amorphous phases of oxides of silicon, aluminum and iron that are formed in the process from the natural minerals associated with the coal.

Owing to its grain structure and pozzolanic reactivity, fly ash has a positive impact on both fresh concrete and hardened concrete: in green concrete, fly ash improves the workability of concrete; in hardened concrete it increases the compressive strength of the concrete and, by contributing to a denser microstructure of the concrete, also improves the durability of the concrete structure.

steament® H-4 fly ash in accordance with DIN EN 450 can be used as Type II addition in concrete subject to DIN 1045-2 / DIN EN 206-1 (national provisions may apply). Fly ash has been used successfully for decades in the concrete producing industry as a high-quality raw material; in designing the concrete composition, the fly ash content may be credited toward the cement content and, via the k-value, towards the water/cement ratio.

The material's high quality is ensured by regular internal quality inspection and monitored by a recognized and independent inspection body. In addition to the Certificate of Conformity issued by **MPA NRW**, the environmental compatibility of **steament® H-4** has been verified in a general technical approval procedure.

In addition to the criteria of DIN EN 450-1, the manufacturer of steament® H-4 has declared compliance with the environmental requirements in accordance with the Model Administrative Regulation (MVV TB) Section A 3.2.3 and the DAfStb Environmental Guideline in its declaration of performance.

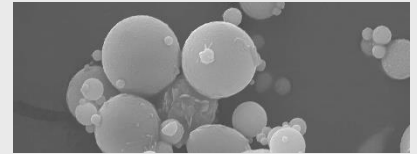

Certificates

Certificate of Conformity:
0432-CPR-00124-01



Product Data

based on a statistic evaluation of the product autocontrol results for the year 2023¹⁾

Parameter	Average		Std. dev.	Requirement
Normative				
Loss on ignition ²⁾ Category A	2.5	M.-%	0.46	≤ 5.0
Fineness > 0,045 mm Category N	24	M.-%	3.4	19 ± 10
CaO _{total}	4.9	M.-%	0.21	≤ 10.0
CaO _{free}	0.3	M.-%	0.06	– ³⁾
SO ₃	1.0	M.-%	0.10	≤ 3.0
Cl	<0.01	M.-%	-	≤ 0.10
Na ₂ O _{equiv.}	1.1	M.-%	0.11	≤ 5.0
Particle density	2.25	g/cm ³	0.04	2.32 ± 0.2
Activity index	28d	83	%	≥ 75
	90d	97	%	≥ 85

- ¹⁾ The data compiled in the table shall not be deemed to be warranted characteristics nor constitute any warranty of quality.
- ²⁾ total carbon (TC)
- ³⁾ from a content greater than 1.5 M.-% the soundness shall be tested

November 2024

EP Power Minerals GmbH
Duisburger Str. 170
46535 Dinslaken, Germany
E-Mail: pqa@ep-pm.com

www.eppowerminerals.com